

The Upper Critical Field for Unconventional Superconducting Film: a Kink due to the Boundary Conditions

Yu.S.Barash, A.V.Galaktionov, and A.A.Svidzinsky

*I.E. Tamm Department of Theoretical Physics, P.N. Lebedev Physics Institute
Leninsky Prospect 53, Moscow 117924, Russia*

Abstract

Boundary conditions for unconventional superconducting order parameter are obtained on the basis of a microscopic theory. The upper critical field in a superconducting film is examined for unconventional superconductors with two-component order parameter and is compared with the case of accidental degeneracy. It is shown, that for both cases temperature dependences of the upper critical field in a superconducting film may depend substantially on the quality of boundaries, and under certain conditions have a kink due to the influence of film boundaries. The location of a kink point appears to be dependent on a film thickness. If for a massive sample there is another reason for the existence of a kink, the interplay of the reasons may lead to a specific behaviour of a kink point location as a function of a temperature or a film thickness. A new test is suggested permitting to distinguish between E_1 and E_2 types of pairing in a hexagonal superconductor near T_c .

PACS numbers: 74.20.De, 74.60.Ec, 74.50.+r, 74.70.Tx

I. INTRODUCTION

The properties of unconventional superconductors are currently widely discussed. In particular, the types of pairing which correspond to two-component superconducting order parameter $\boldsymbol{\eta} = (\eta_1, \eta_2)$ are of interest especially due to the unconventional properties of some heavy-fermion superconducting compounds exemplified by UPt_3 . Another possibility of treating the properties of these compounds is related with the accidental degeneracy, when two different types of pairing (with one-component order parameters η_1 and η_2 correspondingly) have for some reasons very close critical temperatures T_{c1}, T_{c2} (see, for example, [1–4]). Splitting of the superconducting phase transition [5,6], a kink (a change in slope) in $H_{c2}(T)$ and $H_{c1}(T)$ [7–10], several phase transitions within a mixed state [7,11–17] or under the pressure [18] are the important experimental evidences in favour of unconventional pairing in UPt_3 . They can be described to some extent within the framework of several alternative approaches [1,2,19–28]. Though the existence of a tetracritical point on H-T -phase diagram of superconducting UPt_3 at any orientation of a magnetic field leads to failure if one bases on a theory with two-component order parameter, the possibility of two neighbouring critical points (instead of one tetracritical point) is compatible with the theory [2,7,8,15,17,18]. So, for the unambiguous identification of the type of pairing in UPt_3 additional experiments are needed.

In this paper we examine a temperature dependence of the upper critical field in a thin superconducting film, when hexagonal or tetragonal superconductor is supposed to be unconventional with two-component order parameter or with accidentally nearly degenerate order parameters. It will be shown that the influence of film boundaries themselves may result in appearance of a kink in $H_{c2}(T)$ at a temperature $T = T_k$ and the conditions under which it occurs will be determined. The value of T_k depends upon a film thickness. For $T_{c1} \neq T_{c2}$ the kink actually takes place in a massive homogeneous sample as well. The behaviour of the kink in a film in comparison with the one in a homogeneous sample has some distinctive features. Massive superconducting samples of UPt_3 appear in fact to be nonhomogeneous, containing a macroscopic incommensurate structural modulation [29]. Considering a thin film as the simplest example for examining the influence of a nonhomogeneity upon $H_{c2}(T)$, one may come to the conclusion about a possibility of a noticeable contribution of lattice superstructures in UPt_3 to the observable kink of $H_{c2}(T)$. The presence or absence in experiment of the determined below temperature dependence of H_{c2} for thin superconducting film of UPt_3 (or of any other superconductor) could help to identify the type of pairing in the sample.

For a solution of the problem it is necessary to make use of the boundary conditions for the order parameter in unconventional superconductors. This problem is examined in the second section of the paper. For this purpose the microscopic approach is used, based on the quasiclassical Eilenberger equations.

II. BOUNDARY CONDITIONS FOR THE ORDER PARAMETER IN HEXAGONAL UNCONVENTIONAL SUPERCONDUCTORS

The Ginzburg-Landau free energy for a hexagonal unconventional superconductor with strong spin-orbit coupling and with two-component order parameter (η_1, η_2) can be written up to the second order invariants as follows [30,1]:

$$F = \int dV (a\eta_i\eta_i^* + K_1 p_i^* \eta_j^* p_i \eta_j + K_2 p_i^* \eta_i^* p_j \eta_j + K_3 p_i^* \eta_j^* p_j \eta_i + K_4 p_z^* \eta_i^* p_z \eta_i). \quad (1)$$

Here $a = \alpha(T - T_c)$, $p_i = -i\hbar\partial_{x_i} - (2e/c)A_i$. The z axis is directed along the hexagonal crystalline axis. The indices i, j are equal to 1 and 2 and correspond to the x and y components for the operator $\mathbf{p}$. We let $\hbar = 1$ in this Section.

In the case of one-component order parameter the corresponding free energy may be obtained from (1) by setting $\eta_2 = 0$ and $K_2 = K_3 = 0$.

The Ginzburg-Landau equations stemming from (1) should be supplemented by the boundary conditions for the order parameter. These boundary conditions must be consistent with the absence of the current normal to the boundary at the boundary with vacuum. Since $\mathbf{j} = -c\delta F/\delta \mathbf{A}$, the expression for the superconducting current has the structure:

$$\mathbf{j} = -2ie(\eta_1^* \mathbf{h}_1 + \eta_2^* \mathbf{h}_2 - c.c), \quad (2)$$

where $\mathbf{h}_1, \mathbf{h}_2$ are linear combinations of $\partial_i \eta_j$. The condition of the vanishing of the current normal to the boundary can be written as:

$$\begin{cases} h_{1n} = b_{11}\eta_1 + b_{12}\eta_2 \\ h_{2n} = b_{21}\eta_1 + b_{22}\eta_2 \end{cases} \quad (3)$$

The quantities in (3) are taken at the boundary, subscript n denotes the projection on the normal to the boundary $\mathbf{n}$ which is directed inwards for definiteness, $b_{11}, b_{22}, b_{12} = b_{21}$ are real. The boundary conditions (3) are equivalent to ascribing of the effective surface energy to (1) with density $b_{ij}\eta_i^*\eta_j$. Within the Ginzburg-Landau approach b_{ij} are independent upon temperature and they are functions of relative orientation of the crystalline axes and $\mathbf{n}$. The values of b_{ij} must be derived from microscopic equations. This can be done without loss of generality, for instance, in the absence of the external magnetic field and for the order parameter varying only in the perpendicular to the plane boundary direction. It permits to decouple two equations for the two-component order parameter, which substantially simplifies the consideration. Let's denote by l the coordinate along perpendicular to the boundary direction and take $l > 0$ for definiteness. The generalization on the case of the presence of magnetic field and of spatial variation of the order parameter parallel to the boundary is obvious due to (3). Generally speaking, in the absence of the external magnetic field the current parallel to the boundary may flow, so the magnetic field may be induced. Naturally near T_c the account of the internal magnetic field results in corrections to the boundary conditions which are small in the measure of $(T_c - T)/T_c$. So such effects usually may be neglected and we don't take them into account. Below we shall also consider for simplicity the case of the spherical Fermi-surface.

When the pairing is singlet, Eilenberger equations for anisotropic superconductors (see e.g. [31,32]) can be reduced to the following system:

$$\begin{cases} (2\omega_m + \mathbf{v}_F \nabla_{\mathbf{R}})f(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) - 2\Delta(\hat{\mathbf{p}}, \mathbf{R})g(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) = 0 \\ (2\omega_m - \mathbf{v}_F \nabla_{\mathbf{R}})f^+(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) - 2\Delta^*(\hat{\mathbf{p}}, \mathbf{R})g(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) = 0 \\ \mathbf{v}_F \nabla_{\mathbf{R}}g(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) + \Delta(\hat{\mathbf{p}}, \mathbf{R})f^+(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) - \Delta^*(\hat{\mathbf{p}}, \mathbf{R})f(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) = 0 \end{cases} \quad (4)$$

Here $\omega_m = (2m+1)\pi T$ is the Matsubara frequency, $\hat{\mathbf{p}} = \mathbf{p}/|\mathbf{p}|$ is the unit vector in the direction of Fermi momentum, $\mathbf{v}_F(\hat{\mathbf{p}})$ is the Fermi velocity, $\Delta(\hat{\mathbf{p}}, \mathbf{R})$ is the gap function. Anomalous Green functions $f(\hat{\mathbf{p}}, \mathbf{R}, \omega_m)$ and $f^+(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) = f^*(-\hat{\mathbf{p}}, \mathbf{R}, \omega_m)$ and Green function $g(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) = g^*(-\hat{\mathbf{p}}, \mathbf{R}, \omega_m)$ satisfy the normalization condition

$$g^2(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) + f(\hat{\mathbf{p}}, \mathbf{R}, \omega_m)f^+(\hat{\mathbf{p}}, \mathbf{R}, \omega_m) = 1. \quad (5)$$

The equation of self-consistency is:

$$\Delta(\hat{\mathbf{p}}, \mathbf{R}) = -\pi T \sum_m \int \frac{d^2 S'}{(2\pi)^3 v_F} V(\hat{\mathbf{p}}, \hat{\mathbf{p}}') f(\hat{\mathbf{p}}', \mathbf{R}, \omega_m), \quad (6)$$

where $V(\hat{\mathbf{p}}, \hat{\mathbf{p}}')$ is the anisotropic pairing potential and the integration is carried out over the Fermi surface. The system (4) should be supplemented by boundary conditions for quasiclassical propagators [33–35]. If the nonmagnetic impenetrable boundary is specularly reflecting, these boundary conditions take the form:

$$g(\hat{\mathbf{p}}) = g(\check{\mathbf{p}}), \quad f(\hat{\mathbf{p}}) = f(\check{\mathbf{p}}), \quad f^+(\hat{\mathbf{p}}) = f^+(\check{\mathbf{p}}). \quad (7)$$

Here $\hat{\mathbf{p}}$ and $\check{\mathbf{p}}$ denote the incident and reflected momenta correspondingly. According to the mentioned above, expressions for b_{ij} may be derived without loss of generality in the case of the real gap function $\Delta(\hat{\mathbf{p}}, \mathbf{R})$. Then it is natural to introduce $f_1 = (f + f^+)/2$, $f_2 = (f - f^+)/2$. Neglecting higher powers of Δ near T_c , we come from (4) to the following equation:

$$f_1(\hat{\mathbf{p}}, l, \omega_m) - \frac{v_l^2}{4\omega_m^2} \partial_l^2 f_1(\hat{\mathbf{p}}, l, \omega_m) - \frac{\Delta(\hat{\mathbf{p}}, l)}{|\omega_m|} = 0, \quad (8)$$

where v_l is the l -component of the Fermi velocity $\mathbf{v}_F$.

The solution of this equation satisfying the boundary conditions (7) is:

$$f_1(\hat{\mathbf{p}}, l, \omega_m) = \frac{1}{|v_l|} \int_0^\infty \left\{ \exp(-|\frac{2\omega_m}{v_l}||l - l'|) \Delta(\hat{\mathbf{p}}, l') + \exp(-|\frac{2\omega_m}{v_l}||l + l'|) \Delta(\check{\mathbf{p}}, l') \right\} dl'. \quad (9)$$

In the case of one-component order parameter the gap function is supposed to have a factorized form $\Delta(\hat{\mathbf{p}}, \mathbf{R}) = \eta(\mathbf{R})\psi(\hat{\mathbf{p}})$, and for the two-component order parameter the corresponding form is $\Delta(\hat{\mathbf{p}}, \mathbf{R}) = \eta_1(\mathbf{R})\psi_1(\hat{\mathbf{p}}) + \eta_2(\mathbf{R})\psi_2(\hat{\mathbf{p}})$. Thus the symmetry of the gap function in homogeneous superconductor is defined by the symmetry of $\psi_{1,2}(\hat{\mathbf{p}})$. Substituting (9) into (6) we get with account of these representations two integral equations in the case of two-component order parameter:

$$\eta_i(l) = \frac{\pi T \lambda}{\int \psi_i^2(\hat{\mathbf{p}}) d^2 S} \sum_m \int_0^\infty \int d^2 S \psi_i(\hat{\mathbf{p}}) \left\{ \frac{\Delta(\hat{\mathbf{p}}, l')}{|v_l|} \exp(-|\frac{2\omega_m}{v_l}| |l - l'|) + \right. \\ \left. + \frac{\Delta(\check{\mathbf{p}}, l')}{|v_l|} \exp(-|\frac{2\omega_m}{v_l}| (l + l')) \right\} dl'. \quad (10)$$

Here λ is the effective coupling constant in the anisotropic case:

$$\lambda \psi_i(\hat{\mathbf{p}}) = - \int V(\hat{\mathbf{p}}, \hat{\mathbf{p}}') \psi_i(\hat{\mathbf{p}}') \frac{d^2 S'}{(2\pi)^3 v_F}. \quad (11)$$

It is related to the critical temperature T_c by $\pi T_c \lambda \sum_m |\omega_m|^{-1} = 1$. The linearized equations (10) are applicable at the distances less than $\xi(T)$ from the boundary. The function f_2 does not contribute to them being odd in ω_m .

For the case of the one-component order parameter the equation (10) and corresponding boundary conditions for $p_x^2 - p_y^2$ -type of paring in tetragonal superconductor have been recently examined in [36]. For those orientations of the boundary for which the relation $\psi(\hat{\mathbf{p}}) = -\psi(\check{\mathbf{p}})$ holds, the solution of (10) in the case of the one-component order parameter is $\eta(l) = Cl$. Similarly if the order parameter has the property $\psi(\hat{\mathbf{p}}) = \psi(\check{\mathbf{p}})$ the solution of (10) is $\eta(l) = C$. The momenta of electrons reflected from the boundary are related to the incident momenta by the reflection accross the plane parallel to the boundary. Since there are seven planes of symmetry in the symmetry group D_{6h} , we may write the boundary conditions using the characters of the reflections accross these planes (for seven corresponding crystal orientations with the normal to the boundary perpendicular to the plane of symmetry). If the character of the one-dimensional irreducible representation is 1 (-1) the boundary condition is $\eta'(0) = 0$ ($\eta(0) = 0$). When the integral equations for two components of the order parameter decouple, the boundary conditions can be similarly written.

The irreducible representations and corresponding basis functions of D_{6h} are listed in Table I. We assume that the spins in the triplet state are ordered along z axis, this is denoted by the spin matrix $\hat{c}$. In this particular case the equations for the order parameter can be reduced to Eqs.(10) as well.

When the angle θ_0 between the normal to the boundary $\mathbf{n}$ and z axis constitutes $\pi/2$ and the azimuthal angle ϕ_0 (between x and $\mathbf{n}$) equals $k\pi/6$ (k is integer) the boundary conditions for different representations are enlisted in table II. The notations

$$\begin{cases} \tilde{\eta}_1 = \eta_1 \cos \phi_0 + \eta_2 \sin \phi_0 \\ \tilde{\eta}_2 = -\eta_1 \sin \phi_0 + \eta_2 \cos \phi_0 \end{cases} \quad (12)$$

are introduced there for E_{1g}, E_{1u} representations.

Similarly for E_{2g}, E_{2u} representations:

$$\begin{cases} \tilde{\eta}_1 = \eta_1 \cos(2\phi_0) - \eta_2 \sin(2\phi_0) \\ \tilde{\eta}_2 = \eta_1 \sin(2\phi_0) + \eta_2 \cos(2\phi_0) \end{cases} \quad (13)$$

If $\mathbf{n}$ coincides with z we obtain the following boundary conditions for one-dimensional representations and for both components of two-dimensional representations : for A_{1u}, A_{2u} ,

$B_{1g}, B_{2g}, E_{1g}, E_{2u} - \eta(0) = 0$; for the remaining representations $-\eta'(0) = 0$. We see that the microscopic structure of the gap function reveals itself in boundary conditions to the Ginzburg-Landau equations, although these equations may be similar for different representations.

Now let's discuss the solution of Eq.(10) for arbitrary orientations. It is easy to check, that for the basis functions of Table I in the case of spherical Fermi-surface these integral equations decouple, if transformations (12),(13) are applied for E_1, E_2 functions respectively:

$$\begin{aligned} \tilde{\eta}_i(l) = \frac{\pi T \lambda}{\int \tilde{\psi}_i^2(\hat{\mathbf{p}}) d^2 S} \sum_m \int_0^\infty \int d^2 S \tilde{\eta}_i(l') \tilde{\psi}_i(\hat{\mathbf{p}}) \left\{ \frac{\tilde{\psi}_i(\hat{\mathbf{p}})}{|v_l|} \exp(-|\frac{2\omega_m}{v_l}| |l - l'|) + \right. \\ \left. + \frac{\tilde{\psi}_i(\check{\mathbf{p}})}{|v_l|} \exp(-|\frac{2\omega_m}{v_l}| (l + l')) \right\} dl'. \end{aligned} \quad (14)$$

There is no summation over subscript i in this equations and they look exactly like equations for the one-component order parameter. The functions $\tilde{\psi}_i(\hat{\mathbf{p}})$ are related to $\psi_i(\hat{\mathbf{p}})$ by the same equations (12),(13). The gap function may be rewritten as $\Delta(\hat{\mathbf{p}}, l) = \tilde{\psi}_1(\hat{\mathbf{p}}) \tilde{\eta}_1(l) + \tilde{\psi}_2(\hat{\mathbf{p}}) \tilde{\eta}_2(l)$.

At the distances $\xi_0 \ll l \ll \xi(T)$ from the boundary Eq.(14) has a solution $\tilde{\eta}_i(l) = C(l + q_i)$, the value of q_i may be obtained from the variational procedure developed in [37], which usually turns out to be a good approximation. The exact relation for q_i is:

$$\frac{7\zeta(3)q_i\lambda}{\pi^2 T^2} \int \tilde{\psi}_i^2(\hat{\mathbf{p}}) v_l^2 d^2 S = \frac{\pi\lambda}{48T^3} \int \tilde{\psi}_i(\hat{\mathbf{p}}) (\tilde{\psi}_i(\hat{\mathbf{p}}) + \tilde{\psi}_i(\check{\mathbf{p}})) |v_l|^3 d^2 S + [D_{min} \int \tilde{\psi}_i^2(\hat{\mathbf{p}}) d^2 S]^{-1}, \quad (15)$$

where D_{min} is the minimal value of the functional:

$$D = \frac{\int_0^\infty q(l) [q(l) - \int_0^\infty K(l, l') q(l') dl'] dl}{[\int_0^\infty q(l) E(l)]^2}. \quad (16)$$

Here $K(l, l')$ is the kernel of the original integral equation (14) ($\tilde{\eta}_i(l) = \int_0^\infty K(l, l') \tilde{\eta}_i(l') dl'$) and

$$E(l) = \pi T \lambda \sum_m \int \tilde{\psi}_i(\hat{\mathbf{p}}) \frac{(\tilde{\psi}_i(\hat{\mathbf{p}}) + \tilde{\psi}_i(\check{\mathbf{p}})) |v_l|}{\omega_m^2} \exp(-|\frac{2\omega_m}{v_l}| l) d^2 S. \quad (17)$$

The function $q(l)$ in Eq.(16) is supposed to tend to the constant value, when $l \rightarrow \infty$. Estimating (16) for constant $q(l)$ we obtain approximate values of q_i :

$$\begin{aligned} q_i = \left(\frac{\pi^3}{336\zeta(3)T} \int_{v_l > 0} [\tilde{\psi}_i(\hat{\mathbf{p}}) + \tilde{\psi}_i(\check{\mathbf{p}})]^2 v_l^3 d^2 S + \right. \\ \left. + \frac{7\zeta(3)}{4\pi^3 T} \frac{(\int_{v_l > 0} [\tilde{\psi}_i(\hat{\mathbf{p}}) + \tilde{\psi}_i(\check{\mathbf{p}})]^2 v_l^2 d^2 S)^2}{\int_{v_l > 0} [\tilde{\psi}_i(\hat{\mathbf{p}}) - \tilde{\psi}_i(\check{\mathbf{p}})]^2 v_l d^2 S} \right) \left(\int \tilde{\psi}_i^2(\hat{\mathbf{p}}) v_l^2 d^2 S \right)^{-1}, \end{aligned} \quad (18)$$

where the subscript $v_l > 0$ denotes that the integration is made over that part of the Fermi surface, where $v_l > 0$. This equation may be applied for one-dimensional representations

directly for the boundary condition $q\eta'(0) = \eta(0)$ with the non-tilded values η , since no decoupling problem arises in this case. Eq.(18) remains to be valid for complex basis functions as well after simple replacement of squares of the basis functions and of sums and differences of the basis functions by squares of the corresponding moduli.

Particular values of q_i , generally speaking, essentially depend upon the explicit particular form of basis functions $\psi_i(\hat{\mathbf{p}})$, which may differ even if they belong to the same symmetry representation. Only values $q = 0, \infty$ governed by the symmetry are invariant for the given type of pairing (irrespective of the shape of the Fermi-surface of the given symmetry). For the specific basis functions of E_{1g} type from Table I the integration in (18) results in:

$$\begin{aligned} q_1^s &= \frac{v_F}{T_c} \sin^2 2\theta_0 \left(\frac{95\pi^3}{18432\zeta(3)} + \frac{12\zeta(3)}{5\pi^3} \tan^2 2\theta_0 \right), \\ q_2^s &= \frac{v_F}{T_c} \frac{\sin^2 \theta_0}{1 + 2 \cos^2 \theta_0} \left(\frac{5\pi^3}{1536\zeta(3)} + \frac{4\zeta(3)}{5\pi^3} \tan^2 \theta_0 \right). \end{aligned} \quad (19)$$

The boundary condition takes the form $q_i \tilde{\eta}'_i(0) = \tilde{\eta}_i(0)$. So if $\theta_0 = \pi/2, \phi_0 = 0$ we obtain $\eta_1(0) = 0$ (since q_1 vanishes), while $\eta'_2(0) = 0$ (since $q_2 = \infty$). Similarly other orientations from Table II and the case of $\mathbf{n}$ along z may be checked. From (19) it follows that beyond the relatively narrow vicinities $\sim (\xi_0/\xi(T))^{1/2}$ of the directions for which $q_i = \infty$, the parameter q_i has the order of ξ_0 , because near these directions $q_i \sim \xi(0)/(\Delta\theta_0)^2$, where $\Delta\theta_0$ is the angular displacement from these directions.

For the triplet pairing of E_1 -type Eq.(18) and Table I yield:

$$\begin{aligned} q_1^t &= \frac{v_F}{T_c} \frac{\cos^2 \theta_0}{3 \sin^2 \theta_0 + \cos^2 \theta_0} \left(\frac{5\pi^3}{1344\zeta(3)} + \frac{14\zeta(3)}{15\pi^3} \cot^2 \theta_0 \right), \\ q_2^t &= \infty. \end{aligned} \quad (20)$$

If the functions are those from Table I of E_2 type we obtain in the case of singlet pairing:

$$\begin{aligned} q_1^s &= \frac{v_F}{T_c} \frac{\cos^2 \theta_0}{1 + 2 \sin^2 \theta_0} \left(\frac{5\pi^3}{1536\zeta(3)} + \frac{4\zeta(3)}{5\pi^3} \cot^2 \theta_0 \right), \\ q_2^s &= \frac{v_F}{T_c(1 + 2 \sin^2 \theta_0)} \left(\frac{5\pi^3}{6144\zeta(3)} (4 - 4 \sin^2 \theta_0 + 19 \sin^4 \theta_0) + \frac{7\zeta(3)}{5\pi^3} \frac{(3 \sin^4 \theta_0 - \sin^2 \theta_0 + 1)^2}{\sin^2 2\theta_0} \right). \end{aligned} \quad (21)$$

And in the case of triplet pairing:

$$\begin{aligned} q_1^t &= \frac{v_F}{T_c} \sin^2 2\theta_0 \left(\frac{19\pi^3}{4096\zeta(3)} + \frac{32\zeta(3)}{15\pi^3} \tan^2 2\theta_0 \right), \\ q_2^t &= \frac{v_F \sin^2 \theta_0}{T_c(4 + 6 \sin^2 \theta_0 - 15 \sin^4 \theta_0 + 9 \sin^6 \theta_0)} \left(\frac{\pi^3}{1024\zeta(3)} (100 - 276 \sin^2 \theta_0 + 195 \sin^4 \theta_0) + \right. \\ &\quad \left. + \frac{32\zeta(3)}{15\pi^3} \frac{(22 - 59 \sin^2 \theta_0 + 41 \sin^4 \theta_0)^2 \tan^2 \theta_0}{4 - 12 \sin^2 \theta_0 + 27 \sin^4 \theta_0} \right). \end{aligned} \quad (22)$$

The values of q_i enable to write down the surface free energy and then (considering the total free energy) to obtain the general boundary conditions for the Ginzburg-Landau equations, not necessarily for the case, when the order parameter is changing only in the direction normal to the boundary. In the weak coupling limit the gradient terms of the Ginzburg-Landau Hamiltonian, as is known, take the form [38]:

$$F_{grad} = \frac{7\zeta(3)}{16\pi^2 T_c^2} \int (v_i \partial_i \Delta(\hat{\mathbf{p}})) (v_j \partial_j^* \Delta^*(\hat{\mathbf{p}})) \frac{d^2 S}{(2\pi)^3 v_F}. \quad (23)$$

So in the case of spherical Fermi-surface and functions from Table I we get, that for the E_1 -type of pairing $K_1 = K_2 = K_3 = K$, besides in the case of singlet pairing $K_4 = 3K$, while for triplet $K_4 = K$. Taking into account these relations one can find the explicit expressions for h_{1n}, h_{2n} in (3). Then comparing Eq.(3) with the microscopic boundary conditions $q_i \tilde{\eta}'_i(0) = \tilde{\eta}_i(0)$ one obtains the coefficients b_{ij} resulting in the following expressions for the surface free energy:

$$F_{surf}^s = \frac{3K}{q_1^s(\theta_0)} |\eta_1 \cos \phi_0 + \eta_2 \sin \phi_0|^2 + \frac{K(\sin^2 \theta_0 + 3 \cos^2 \theta_0)}{q_2^s(\theta_0)} |\eta_2 \cos \phi_0 - \eta_1 \sin \phi_0|^2, \\ F_{surf}^t = \frac{K(3 \sin^2 \theta_0 + \cos^2 \theta_0)}{q_1^t(\theta_0)} |\eta_1 \cos \phi_0 + \eta_2 \sin \phi_0|^2. \quad (24)$$

Here $q_i^{s,t}$ are given by (19),(20) respectively. Note, that free energy is written down in terms of original η_1, η_2 .

If the pairing is of E_2 type, then for the spherical Fermi-surface one has $K_2 = K_3 = 0$ and $K_4 = K/3$ ($K_4 = K$) for singlet (triplet) pairing. Thus the surface free energy acquires the form:

$$F_{surf}^s = K \left(\sin^2 \theta_0 + \frac{\cos^2 \theta_0}{3} \right) \left\{ \frac{1}{q_1^s(\theta_0)} |\eta_1 \cos 2\phi_0 - \eta_2 \sin 2\phi_0|^2 + \frac{1}{q_2^s(\theta_0)} |\eta_2 \cos 2\phi_0 + \eta_1 \sin 2\phi_0|^2 \right\}, \\ F_{surf}^t = K \left\{ \frac{1}{q_1^t(\theta_0)} |\eta_1 \cos 2\phi_0 - \eta_2 \sin 2\phi_0|^2 + \frac{1}{q_2^t(\theta_0)} |\eta_2 \cos 2\phi_0 + \eta_1 \sin 2\phi_0|^2 \right\}. \quad (25)$$

Like the specific values of the parameter q_i , the particular form of the orientational dependence of the surface free energy is governed by the explicit particular form of the basis functions. Any angular dependence of q_i and F_{surf} can be certainly expressed in terms of n_i^2 , i.e. $\sin^2 \theta_0 = n_x^2 + n_y^2$. The surface free energy can be represented as a simple quadratic form over n_x^2, n_y^2, n_z^2 for a special kind of basis functions only. According to (24),(25) higher powers of n_i^2 are also involved in the expression for F_{surf} for the basis functions from Table I. If the free energy (1) is invariant under the rotations on arbitrary angles around z -axis and q_i depend only upon θ_0 , one can write down volume and surface free energies in a ϕ_0 -independent form simultaneously. It takes place for a particular choice of basis functions for two-dimensional representations indicated in Table I and for rotationally invariant Fermi surface. So, in the particular cases (1), (24) or (25) the boundary conditions in fact do not result in a ϕ_0 -dependence, since $\tilde{\eta}_i$ can be used in the total free energy. One can easily demonstrate that for both two-dimensional representations there are basis functions breaking rotational symmetry of the total free energy functional.

If the value of q_i is of the order of ξ_0 , we have $\tilde{\eta}_i(0) \sim \tilde{\eta}_{i\infty}(\xi_0/\xi(T)) \ll \tilde{\eta}_{i\infty}$ at the boundary, where $\tilde{\eta}_{i\infty}$ is the value in the depth of the superconductor. So near T_c we can set approximately $\tilde{\eta}_i(0) = 0$. Hence, as it follows from (19), (21), (22), the prevailing boundary condition (i.e. for the most of orientations of the boundary) for E_2 -type of symmetry (both triplet and singlet) and for singlet pairing of E_1 - type is:

$$\eta_1(0) = \eta_2(0) = 0. \quad (26)$$

For the specific triplet basis functions of E_1 -type from Table I the prevailing boundary condition is:

$$\tilde{\eta}_1(0) = \tilde{\eta}'_2(0) = 0, \quad (27)$$

but if other basis functions without rotational symmetry are used, or non-spherical Fermi-surface is considered, the prevailing boundary condition will be Eq.(26) for this case as well.

If the scattering at the boundary is diffusive, rather than specular, the appropriate values of q_i will be of the order of ξ_0 as is shown in [39], so we can use Eq.(26) as a good approximation near T_c for all orientations in this case (and for all anisotropic pairings irrespective of the crystalline symmetry).

III. TWO-COMPONENT ORDER PARAMETER: $H_{C2}(T)$ FOR A SUPERCONDUCTING FILM

Let the crystal axis of high symmetry (axis z) be parallel to the boundary of a film with thickness $2d$, axis x be perpendicular to the film surface and a magnetic field $\mathbf{H} \parallel x$ (see fig.1). Though our goal is to describe some properties of a hexagonal superconductor UPt_3 as one of a probable candidate for a two-component unconventional superconductor, there are some formal reasons (associated with the simplifying of the problem) to consider firstly a more general case of a tetragonal superconductor. Besides the case of a tetragonal unconventional superconductor is of interest as itself, since the question about the type of pairing remains unsolved also in some tetragonal heavy fermion superconductors like $CeCu_2Si_2$ and URu_2Si_2 . Then the Ginzburg-Landau free energy up to the second order terms reads

$$F = \int \int dydz \left\{ \int_{-d}^d dx \left[a\eta_i\eta_i^* + K_1 p_i^* \eta_j^* p_i \eta_j + K_2 p_i^* \eta_i^* p_j \eta_j + K_3 p_i^* \eta_j^* p_j \eta_i + K_4 p_z^* \eta_i^* p_z \eta_i + \right. \right. \\ \left. \left. + K_5 (|p_x \eta_2|^2 + |p_y \eta_1|^2) \right] + S_1 (|\eta_1|^2|_{x=-d} + |\eta_1|^2|_{x=d}) + S_2 (|\eta_2|^2|_{x=-d} + |\eta_2|^2|_{x=d}) \right\} \quad (28)$$

The terms describing the surface contribution to the free energy in Eq.(28), correspond to taking into account the boundary conditions for the order parameter. We have not written one more surface term $S_3(\eta_1\eta_2^* + \eta_1^*\eta_2)$ since for the given orientation of crystal axes relative to the film boundary one has $S_3 = 0$. The coefficients S_1, S_2, S_3 may be determined by

comparing the boundary conditions following from (28) with those based on a microscopic theory.

It is convenient to choose the vector potential in the form $A_z = Hy$ and to introduce dimensionless quantities $\varepsilon = (K_2 + K_3)/K$, $\mu = (K_2 - K_3)/K$, $\zeta = 2K_4/K$, $\nu = (K_2 + K_3 - K_5)/K$, $\tilde{a} = -ac\zeta^{1/2}/(2\hbar K_4|e|H)$, $\tilde{S}_{1,2} = 2S_{1,2}l/(\hbar^2 K)$, $x \rightarrow xl$, $y \rightarrow yl$, $z \rightarrow zl$, where $K = 2K_1 + K_2 + K_3 + K_5$, $l = \zeta^{-1/4}(\hbar c/2|e|H)^{1/2}$. Then Eq.(28) is transformed as follows

$$F = \frac{1}{2}K\hbar^2l \int dydz \left\{ \int_{-L}^L dx [-\tilde{a}(|\eta_1|^2 + |\eta_2|^2) + (1 + \nu)(|\partial_x \eta_1|^2 + |\partial_y \eta_2|^2) + (1 - \nu)(|\partial_x \eta_2|^2 + |\partial_y \eta_1|^2) + y^2(|\eta_1|^2 + |\eta_2|^2) + (\varepsilon + \mu)(\partial_x \eta_1^* \partial_y \eta_2 + c.c.) + (\varepsilon - \mu)(\partial_x \eta_2^* \partial_y \eta_1 + c.c.)] + \tilde{S}_1 (|\eta_1|^2|_{x=-L} + |\eta_1|^2|_{x=L}) + \tilde{S}_2 (|\eta_2|^2|_{x=-L} + |\eta_2|^2|_{x=L}) \right\} \quad (29)$$

Here $2L = 2d/l$ is a dimensionless film thickness. One should take into account that for the given gauge of $\mathbf{A}$ it is possible to choose the order parameter $\boldsymbol{\eta} = (\eta_1, \eta_2)$ to be independent of z in considering the upper critical field (it corresponds to the choice of the origin at the y -axis).

Variation of the free energy functional (29) on η_1^*, η_2^* results in the equations

$$\begin{cases} \left[-(1 + \nu)\partial_x^2 + y^2 - (1 - \nu)\partial_y^2 \right] \eta_1 - 2\varepsilon\partial_{xy}\eta_2 = \tilde{a}\eta_1 \\ \left[-(1 - \nu)\partial_x^2 + y^2 - (1 + \nu)\partial_y^2 \right] \eta_2 - 2\varepsilon\partial_{xy}\eta_1 = \tilde{a}\eta_2 \end{cases} \quad (30)$$

and in the boundary conditions

$$\begin{cases} \left((1 + \nu)\partial_x \eta_1 + (\varepsilon + \mu)\partial_y \eta_2 \pm \tilde{S}_1 \eta_1 \right)_{|x=\pm L} = 0 \\ \left((1 - \nu)\partial_x \eta_2 + (\varepsilon - \mu)\partial_y \eta_1 \pm \tilde{S}_2 \eta_2 \right)_{|x=\pm L} = 0 \end{cases} \quad (31)$$

Due to linearity of Eqs.(30, 31) one can consider only those solutions which are characterized by the definite values of parities relative to the independent inversions of x and y axes. Then it is easy to see that the components η_1 and η_2 belonging to the same solution of Eqs.(30, 31), have opposite values of parities both on x and on y .

The condition of positive definiteness of the sum of the gradient terms in (29) results in the following restrictions

$$1 \pm \nu > |\varepsilon \pm \mu| \quad , \quad \zeta > 0 \quad (32)$$

In particular, it follows from (32) that $|\varepsilon| < 1$, $|\mu| < 1$, $|\nu| < 1$. Thus one can usually regard the parameters ε, μ, ν as quite small (for the majority of their admissible values). We shall employ below the perturbation theory up to the second order in ε for the solution of the problem of the upper critical field for the film. For a hexagonal crystal one has $K_5 = 0$ and hence $\nu = \varepsilon$. However, for the simplest qualitative examining of the problem it is convenient to assume the parameters ν and ε to be independent and consider only ε as a small quantity. It is, generally speaking, possible for a tetragonal crystal. The problem of determining of the minimal eigenvalue $\tilde{a}$ will be solved for specular interfaces and for diffusive boundaries separately.

A. Specularly reflecting film surfaces

Since yz -plane is a symmetry plane both for the symmetry group D_{6h} and for D_{4h} , for a given crystal orientations and two-dimensional representations of those groups specularly reflecting film boundaries correspond to the limit $\tilde{S}_1 \rightarrow +\infty$, $\tilde{S}_2 = 0$ in a phenomenological Eq.(31). Then the boundary conditions read

$$\eta_{1|x=\pm L} = 0 \quad , \quad \partial_x \eta_{2|x=\pm L} = 0 \quad (33)$$

The solutions of Eq.(30) with boundary conditions (33) can be represented as follows

$$\begin{cases} \eta_{1n} = \cos(k_n x + \varphi_n) \eta_{1n}(y) \\ \eta_{2n} = \sin(k_n x + \varphi_n) \eta_{2n}(y) \end{cases} \quad n = 0, \pm 1, \pm 2, \dots \quad (34)$$

where $k_n = (\pi/2L)n$, $\varphi_n = (\pi/2)(n+1)$ and functions $\eta_{1n}(y)$, $\eta_{2n}(y)$ must satisfy the system of equations

$$\begin{cases} (y^2 - (1 - \nu)\partial_y^2) \eta_{1n}(y) - 2\varepsilon k_n \partial_y \eta_{2n}(y) = (\tilde{a} - k_n^2(1 + \nu)) \eta_{1n}(y) \\ (y^2 - (1 + \nu)\partial_y^2) \eta_{2n}(y) + 2\varepsilon k_n \partial_y \eta_{1n}(y) = (\tilde{a} - k_n^2(1 - \nu)) \eta_{2n}(y) \end{cases} \quad n \neq 0 \quad (35)$$

$$(y^2 - (1 + \nu)\partial_y^2) \eta_{20}(y) = \tilde{a} \eta_{20}(y) \quad , \quad n = 0 \quad (36)$$

The problem of the upper critical field becomes especially simple and transparent in the zero order approximation in the parameter ε , when Eqs.(35) for η_{1n} , η_{2n} decouple. From the right sides of Eqs.(35) one can see, that dependence of any component of the order parameter upon x results in decreasing of corresponding “critical temperature” T_n (as compared to T_c in the absence of a field). As a result all the quantities $H_n(T)$, following from (35) for $n \neq 0$ as candidates for the upper critical field, describe the magnetic fields decreasing with increasing temperature and vanishing at $T_n < T_c$. Furthermore, it follows from the equations for η_{2n} that the maximum value of magnetic field is reached for the equation (36) with $n = 0$, since $\tilde{a}, k_n^2 \propto 1/H$ and $\nu < 1$. As $T_0 = T_c > T_n$ ($n \neq 0$) the corresponding magnetic field $H_0(T)$ must coincide with H_{c2} close enough to T_c . Then one has for the slope of the upper critical field $H'_{c2} \propto 1/(1 + \nu)^{1/2}$. At the same time it follows from the equations for $\eta_{1n}(y)$ that the slopes of corresponding temperature dependent magnetic fields $\propto 1/(1 - \nu)^{1/2}$. Hence for $\nu > 0$ these magnetic fields increase with decreasing of temperature faster than the field $H_0(T)$, defined by (36). Since the equation with $n = 1$ leads to the maximum admissible value of the magnetic field among all the equations for η_{1n} ($n \neq 0$), one comes eventually to the following result at $\varepsilon = 0$. In the case $\nu < 0$ and for the specularly reflecting boundaries the upper critical field for the film coincides with the one for the massive sample for all temperatures and is described according to (36):

$$H_{c2}(T) = \frac{\Phi_0}{2\pi\xi^2(T)\sqrt{\zeta(1 + \nu)}} \quad (37)$$

where $\xi^2(T) = \hbar^2 K/2|a| = \xi_0^2/(1 - T/T_c)$, $\Phi_0 = \pi\hbar c/|e|$.

But as far the case $\nu > 0$ is concerned the expression (37) describes the upper critical field only within the certain temperature interval $T_k^{(0)} < T < T_c$, and for $T \leq T_k^{(0)}$ the curve $H_{c2}(T)$ suffers a kink and is described as follows

$$H_{c2}^{(0)}(T) = \frac{\Phi_0}{2\pi\xi_0^2\sqrt{\zeta(1-\nu)}} \left(1 - \frac{T}{T_c} - \frac{\pi^2\xi_0^2}{4d^2}(1+\nu) \right) \quad (38)$$

For the point of kink $T_k^{(0)}$ one has from (37), (38)

$$T_k^{(0)} = T_c \left[1 - \frac{\pi^2\xi_0^2}{4d^2} \frac{(1+\nu)^{3/2}}{(\sqrt{1+\nu} - \sqrt{1-\nu})} \right] \quad (39)$$

In order to satisfy the condition $|T_k^{(0)} - T_c| \ll T_c$ the inequality $d^2\nu \gg \xi_0^2$ must hold.

Since the solutions with $n = 0$ and $n = 1$ have a different symmetry— opposite parities relative to the inversions on x and on y — for any value of ε (and not only for $\varepsilon = 0$), it is obvious that the kink at the curve $H_{c2}(T)$ must remain in the case $\varepsilon \neq 0$ as well (for the given orientations of magnetic field and crystal axes). In the case $\varepsilon \neq 0$ the quantitative consideration of the problem becomes more complicated. However, as for hexagonal superconductors $\nu = \varepsilon$, it should be carried out in order to describe the effects in question correctly. Corresponding calculations are represented in Appendix. According to the solution of Eq.(35) for $\varepsilon \neq 0$, the slope $H_1'(T)$ becomes temperature dependent even within the region of applicability of the Ginzburg-Landau theory $T_c - T \ll T_c$. At $T_k \leq T \leq T_c$ the slope coincides with the bulk result (37). At $T \leq T_k$ one gets in accordance with (A.25) up to the second order terms in the parameter ε inclusively

$$1 - \frac{T}{T_c} = \frac{2\pi\xi^{1/2}\xi_0^2}{\Phi_0} \left((1-\nu)^{1/2}H + \frac{\pi\Phi_0}{8\xi^{1/2}d^2} \left(1 + \nu - \frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 \frac{dt}{(1-C^2t^2)^{3/2}} t^{\beta(\nu)-\gamma(\nu,H)} \right) \right) \quad (40)$$

where

$$C = \left| \frac{\sqrt{1+\nu} - \sqrt{1-\nu}}{\sqrt{1+\nu} + \sqrt{1-\nu}} \right|, \quad \beta = \frac{1}{2} \left(1 - \sqrt{\frac{1-\nu}{1+\nu}} \right), \quad \gamma(\nu, H) = \frac{\pi\nu\Phi_0}{8\xi^{1/2}d^2(1+\nu)^{1/2}H} \quad (41)$$

Under the condition $\varepsilon^2, |\nu| \ll L^2 = 2\pi d^2 \xi^{1/2} H_1(T)/\Phi_0$ the upper critical field below the kink temperature T_k takes the form

$$H_{c2}(T) = \frac{\Phi_0}{2\pi\xi_0^2\xi^{1/2}\sqrt{1-\nu}} \left[1 - \frac{T}{T_c} - \frac{\pi^2\xi_0^2}{4d^2} \left(1 + \nu - \frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 \frac{dy y^{\beta(\nu)}}{(1-C^2y^2)^{3/2}} \right) \right] \quad (42)$$

In the limit $\varepsilon^2/L^2 \rightarrow 0$, $\nu/L^2 \rightarrow 0$ the expression (42), becomes exact.

The crossing point of the right lines (37), (42) is

$$\left\{ \begin{array}{l} T_k = T_c \left\{ 1 - \frac{\pi^2 \xi_0^2}{4d^2} \frac{\sqrt{1+\nu}}{\sqrt{1+\nu} - \sqrt{1-\nu}} \left(1 + \nu - \frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 \frac{dy y^{\beta(\nu)}}{(1-C^2 y^2)^{3/2}} \right) \right\} \\ H_k = \frac{\pi \Phi_0}{8d^2 \zeta^{1/2}} \frac{1}{\sqrt{1+\nu} - \sqrt{1-\nu}} \left(1 + \nu - \frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 \frac{dy y^{\beta(\nu)}}{(1-C^2 y^2)^{3/2}} \right) \end{array} \right\} \quad (43)$$

It is assumed in (43) that the kink point (T_k, H_k) lies in the region where the curve $H_1(T)$ nearly coincides with its asymptotic straight line. It is valid if $\Phi_0 \varepsilon^2 / (2\pi d^2 \zeta^{1/2}) \ll H_k$ which in fact is equivalent to the condition $\nu \varepsilon^2 \ll 1$. For $\varepsilon = \nu$ the Eqs. (37), (42), (43) describe the upper critical field in the film for a hexagonal unconventional superconductor with two-component order parameter. The corresponding dependence of $H_{c2}(T)$ is presented in fig.2 (line 1).

Considering the upper critical field for some other orientations of crystalline axes and then comparing the result with one described just now, one can get several simple tests for identification of one or another type of pairing. For instance, one can distinguish between the order parameters transforming according two-dimensional representations E_{1g}, E_{1u} and E_{2g}, E_{2u} , by examining the temperature dependence of the upper critical field near T_c in the film with specularly reflecting boundaries for two different orientations. Since for a hexagonal crystal the x- and y-directions within the basal plane, generally speaking, are not equivalent, let now axis y be perpendicular to the film surfaces, axis x be parallel to the boundary and a magnetic field $\mathbf{H} \parallel y$. The results for this particular case can be readily obtained from the expressions (37), (40), if one takes into account that initial Eqs.(30), (33) must be transformed to the case along the following way. In the Ginzburg-Landau equations (30), written in the crystalline coordinate system, the only modification to the present case is the substitution $y^2 \rightarrow x^2$, which corresponds to the field direction along the y crystalline axis. However, as far as the boundary conditions (33) are concerned, different modifications should be used for the representations E_{1g}, E_{1u} and E_{2g}, E_{2u} . In the case of the representations E_{1g}, E_{1u} the order parameter components, according to Eqs.(12) at $\phi_0 = \pi/2$, must be interchanged in the boundary conditions (33) along with $\partial_x \rightarrow \partial_y$. Then the resulting equations combined with the boundary conditions exactly coincide with the initial ones after the formal substitution $x \leftrightarrow y, \eta_1 \leftrightarrow \eta_2$. Hence the upper critical field remains the same for both orientations in the case of E_{1g}, E_{1u} - representations, but it is not the case for the representations E_{2g}, E_{2u} . Indeed, according to Eqs.(13) at $\phi_0 = \pi/2$ in the latter case the boundary conditions take the same form (33) but for the substitution $\partial_x \rightarrow \partial_y$. Then after the formal substitution $x \rightarrow y, y \rightarrow -x$ the resulting equations differ from the initial equations only by the sign of ε and ν (for a hexagonal crystal $\nu = \varepsilon$). Since as was shown above, for specularly reflecting boundaries the kink occurs only in the case $\nu > 0$, we are coming to the assertion that if the order parameter transforms according to the representations E_{2g}, E_{2u} , the kink must be present for one of the orientations and be absent for the other. This statement holds also for $\phi_0 = (2k+1)\pi/6$, where $k = 0, 1, 2, \dots$

For the specific case of a tetragonal superconductor with two-component order parameter one can similarly suggest the following test permitting to distinguish relative signs of the parameters ε and ν . Indeed, let the normal to the boundary $\mathbf{n}$ lie between the crystalline

axes x, y constituting angle $\pi/4$ with each of them, and $\mathbf{H} \parallel \mathbf{n}$. The film boundary coincides in this case with one of the symmetry planes of the group D_{4h} . One can show, that the Ginzburg-Landau equations and the boundary conditions for this particular crystal orientation are exactly the same as Eqs.(30), (33) after the substitution $\nu \leftrightarrow \varepsilon$, if they are written for the functions $\eta_1 \pm \eta_2$ in the variables $(x \pm y)/\sqrt{2}$. Then, if the parameters ν and ε have opposite signs, the kink in the temperature dependence of $H_{c2}(T)$ occurs only for one of the orientations. In the other case, when the parameters are of the same sign the kink is present (absent) for both orientations simultaneously for $\nu > 0$ ($\nu < 0$).

Let now temperatures T_{c1} and T_{c2} in coefficients $a_i = \alpha(T - T_{c,i})$, $i = 1, 2$ be not equal to each other and $\Delta T_c = |T_{c1} - T_{c2}| \ll T_{c1}$. Then one has instead of $a(|\eta_1|^2 + |\eta_2|^2)$ the terms $a_1|\eta_1|^2 + a_2|\eta_2|^2$ in the expression (28) for the free energy. Similar to consideration given above one can get that at $T_{c1} < T_{c2}$ and $\nu > 0$ the kink of the curve $H_{c2}(T)$ occurs both in a massive homogeneous sample and in a film. The boundary conditions significantly influence the kink location in the case $\xi_0^2/d^2 \gtrsim \Delta T_c/T_c$. On the other hand at $T_{c1} > T_{c2}$ and $\nu > 0$ the kink doesn't exist in a massive homogeneous sample but appears in a sufficiently thin film when $T_1(d) < T_{c2}$. Furthermore in the case $\nu < 0$ and $T_{c1} < T_{c2}$ there is no kink of $H_{c2}(T)$ both in a massive homogeneous sample and in a thin film. At last in the case $\nu < 0$ and $T_{c1} > T_{c2}$ there is a kink in a massive homogeneous sample while it is not present in the case of sufficiently thin film (at $T_1(d) < T_{c2}$).

B. Diffusive electron scattering from the boundaries

While under the condition of a specular reflection of electrons the kink of $H_{c2}(T)$ exists only in the case $\nu > 0$, it will be shown below that in the case of diffusively scattering film boundaries the kink of $H_{c2}(T)$ always takes place no matter what is a value (and a sign) of the parameter ν . This assertion can be easily understood qualitatively from the following simple consideration.

According to the results of Section II, in the case of diffusively scattering film boundaries the boundary conditions read

$$\eta_1|_{x=\pm L} = 0 \quad , \quad \eta_2|_{x=\pm L} = 0 \quad (44)$$

In zero-order approximation in a small parameter ε the equations (30) decouple and their solutions with account of the boundary conditions (44) can be represented in the form $\eta_{i,n}^{(0)}(x, y) = \cos(k_n x + \phi_n) \eta_{i,n}^{(0)}(y)$. Solutions for $\eta_{2n}^{(0)}(x, y)$ may be obtained from the solutions $\eta_{1n}^{(0)}(x, y)$ by changing $\nu \rightarrow -\nu$. In contrast to (33) the boundary conditions (44) don't allow the value $n = 0$ to be admissible both for η_{1n} and for η_{2n} . Then the least changing of a critical temperature due to the boundary conditions is realized for $n = 1$ and is proportional to a corresponding coefficient in front of the term with the second order derivative over the coordinate x in Eq.(30), so that

$$\frac{T_c - T_1}{T_c - T_2} = \frac{1 + \nu}{1 - \nu} \quad (45)$$

On the other hand one can see from the equations for $\eta_1^{(0)}$ and $\eta_2^{(0)}$ that a ratio of slope $H_1^{(0)'}(T)$ (for $\eta_1^{(0)}$) to a slope $H_2^{(0)'}(T)$ (for $\eta_2^{(0)}$) is

$$\frac{H_1^{(0)'}(T)}{H_2^{(0)'}(T)} = \left(\frac{1+\nu}{1-\nu} \right)^{1/2} \quad (46)$$

Thus at $\nu > 0$ the field $H_2(T)$ drops to zero at temperature T_2 greater than T_1 which corresponds in turn to zero value of the field $H_1(T_1)$. However, since a slope $H_1^{(0)'}(T)$ has a greater steepness there appears a crossing of curves $H_1^{(0)}(T)$ and $H_2^{(0)}(T)$ which results in the kink of $H_{c2}(T)$. Under the condition $\nu < 0$ one gets from (45), (46) $T_2 < T_1$ while $|H_2^{(0)'}(T)| > |H_1^{(0)'}(T)|$. It leads again to the crossing of the curves $H_1^{(0)}(T)$ and $H_2^{(0)}(T)$, and hence to the appearing of the kink. Thus in zero-order approximation in the parameter ε it follows from Eqs. (35), (44)

$$H_{c2}^{(0)}(T) = \frac{\Phi_0}{2\pi\xi_0^2\zeta^{1/2} [1 + |\nu| \operatorname{sgn}(T - T_k^{(0)})]^{1/2}} \left[1 - \frac{T}{T_c} - \frac{\pi^2\xi_0^2}{4d^2} (1 - |\nu| \operatorname{sgn}(T - T_k^{(0)})) \right] \quad (47)$$

$$\begin{cases} T_k^{(0)} = T_c \left[1 - \frac{\pi^2\xi_0^2}{4d^2} (2 + \sqrt{1-\nu^2}) \right] \\ H_k^{(0)} = \frac{\pi\Phi_0}{8d^2\zeta^{1/2}} [\sqrt{1+\nu} + \sqrt{1-\nu}] \end{cases} \quad (48)$$

As it follows from Appendix (see (A.31)), for $\varepsilon \neq 0$ the temperature dependence of the upper critical field is described up to the second order terms in ε inclusively by the equation

$$1 - \frac{T}{T_c} = \frac{2\pi\zeta^{1/2}\xi_0^2}{\Phi_0} (1 + \tilde{\nu})^{1/2} H + \frac{\pi^2\xi_0^2}{4d^2} \left(1 - \tilde{\nu} - \frac{4\varepsilon^2(1-C^2)^{3/2}}{\pi^2(1-\nu^2)^{1/2}} \int_0^1 dt \frac{t^{\beta(-\tilde{\nu})}}{(1-C^2t^2)^{3/2}} \sum_{k=1}^{\infty} \frac{k^2}{(k^2 - \frac{1}{4})^2} t^{\delta(k, \tilde{\nu})} \right), \quad (49)$$

where $\tilde{\nu} = |\nu| \operatorname{sgn}(T - T_k)$, $\delta(k, \tilde{\nu}) = \pi\Phi_0\sqrt{1-\tilde{\nu}} \left(4k^2 \frac{1+\tilde{\nu}}{1-\tilde{\nu}} - 1 \right) / (16\zeta^{1/2}d^2H)$.

Thus at $\varepsilon \neq 0$ and diffusively scattering boundaries the upper critical field $H_{c2}(T)$ exhibits a feebly marked nonlinear temperature dependence (in measure of the parameter ε^2 usually multiplied by a small numerical factor) for any sign of ν . Under the condition $1 \ll L^2 = 2\pi\zeta^{1/2}d^2H/\Phi_0$ one can get the exact asymptotic behaviour for the upper critical field

$$H_{c2}(T) = \frac{\Phi_0}{2\pi\zeta^{1/2}\xi_0^2(1+\tilde{\nu})^{1/2}} \left(1 - \frac{T}{T_c} - \frac{\pi^2\xi_0^2}{4d^2} \left(1 - \tilde{\nu} - \frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 dt \frac{t^{\beta(-\tilde{\nu})}}{(1-C^2t^2)^{3/2}} \right) \right) \quad (50)$$

For $T < T_k$ Eq.(50) completely coincides with the asymptotic expression (42) obtained for the case of specularly reflecting boundaries.

In the opposite limit $1 \gg L^2$ one has up to the second order terms in ε inclusively (see (A.37))

$$H_{c2}(T) = \frac{\Phi_0}{2\pi\zeta^{1/2}\xi_0^2(1+\tilde{\nu})^{1/2}} \frac{\left(1 - \frac{T}{T_c} - \frac{\pi^2\xi_0^2}{4d^2}(1-\tilde{\nu})\right)}{\left(1 - \frac{\varepsilon^2}{(1+\tilde{\nu})\tilde{\nu}} \left(1 - \frac{2\sqrt{1-\nu^2}}{\pi\tilde{\nu}} \cot\left(\frac{\pi}{2}\sqrt{\frac{1-\tilde{\nu}}{1+\tilde{\nu}}}\right)\right)\right)} \quad (51)$$

In Eq.(51), which is applicable just below T_c , $\tilde{\nu}$ may be changed on ν since it follows from (48) that the kink point lies at $L \sim 1$.

The temperature dependence of $H_{c2}(T)$, described by (49) is presented in fig.2 (line 2).

If $T_{c1} \neq T_{c2}$ then, like in the case of specularly reflecting boundaries, one can easily compare the conditions for the presence or absence of a kink of $H_{c2}(T)$ in a massive homogeneous sample and in a thin film with diffusively scattering boundaries. A distinction from the case of specular reflection appears here at $\nu < 0$. Then for $T_{c1} < T_{c2}$ the kink is absent in a massive homogeneous sample, but takes place in a sufficiently thin film with $T_1(d) > T_2(d)$. For $T_{c1} > T_{c2}$ and $\nu < 0$ a kink occurs for the both cases.

IV. $H_{C2}(T)$ FOR A SUPERCONDUCTING FILM IN THE CASE OF ACCIDENTAL DEGENERACY

In the case of accidental degeneracy two one-component superconducting order parameters with different symmetry properties correspond to critical temperatures T_{c1} , T_{c2} , which are very close to each other ($|T_{c1} - T_{c2}| = \Delta T_c \ll T_{c1}$). The Ginzburg-Landau functional for uniaxial superconductor in such a situation may be represented up to the second order invariants as follows

$$F = \int dydz \left\{ \int_{-d}^d dx \left[a_1 |\eta_1|^2 + a_2 |\eta_2|^2 + K(|p_x \eta_1|^2 + |p_y \eta_1|^2) + K'(|p_x \eta_2|^2 + |p_y \eta_2|^2) + K_4 |p_z \eta_1|^2 + K'_4 |p_z \eta_2|^2 \right] + S_1 (|\eta_1|_{|x=-d}^2 + |\eta_1|_{|x=d}^2) + S_2 (|\eta_2|_{|x=-d}^2 + |\eta_2|_{|x=d}^2) \right\} \quad (52)$$

Here $a_1 = \alpha_1 (T - T_{c1})$, $a_2 = \alpha_2 (T - T_{c2})$. The coherence lengths $\xi_{0\parallel}^2 = \hbar^2 K / \alpha_1 T_{c1}$, $\xi_{0\perp}^2 = \hbar^2 K_4 / \alpha_1 T_{c1}$, $\xi_{0\parallel}'^2 = \hbar^2 K' / \alpha_2 T_{c2}$, $\xi_{0\perp}'^2 = \hbar^2 K'_4 / \alpha_2 T_{c2}$ will be used below.

In contrast to (28), where there are gradient terms containing $\partial_x \eta_i \partial_y \eta_j$ with $i \neq j$, the terms of such kind are absent in (52). In consequence of this fact two Ginzburg-Landau equations for η_1 and η_2 decouple, if the terms of the fourth order are neglected in the expression for the free energy. This circumstance essentially simplifies the problem of the upper critical field in a film. Let's consider the same as in a previous section orientations of the crystalline axes and of the magnetic field relative to the film boundaries, and the same gauge for the vector-potential $A_z = Hy$. Let the boundary conditions for the order parameters η_1 , η_2 be [40]

$$\eta_1|_{x=\pm d} = 0, \quad \partial_x \eta_2|_{x=\pm d} = 0 \quad (53)$$

According to the results of Sec.II, these boundary conditions are realized for the given orientations, in particular, for specularly reflecting boundaries of a hexagonal superconductor, if the order parameter η_1 corresponds to one of the one-dimensional irreducible representations $A_{2g}, A_{2u}, B_{2g}, B_{2u}$ of D_{6h} and the order parameter η_2 - to one of the representations $A_{1g}, A_{1u}, B_{1g}, B_{1u}$.

The upper critical field may be represented as $H_{c2} = \max(H_1(T), H_2(T))$, where the linear functions of temperature $H_1(T)$ and $H_2(T)$ are associated with the solutions of the Ginzburg-Landau equations $\eta_1 = 0$, $\eta_2 = \eta_{20}(y)$ and $\eta_1 = \cos(\pi x/2d)\eta_{10}(y)$, $\eta_2 = 0$ respectively. Here $\eta_{10}(y)$ and $\eta_{20}(y)$ are related to the zero Landau levels of corresponding equations, and $H_1(T)$, $H_2(T)$ – the appropriate magnetic fields.

Firstly neglecting the difference between T_{c1} and T_{c2} , one has $T_2 = T_c$ and $\Delta T_1 = T_c - T_1 \propto \xi_{0\parallel}^2$. Then $H'_1(T)/H'_2(T) = \xi'_{0\perp}\xi'_{0\parallel}/\xi_{0\perp}\xi_{0\parallel}$. Thus the inclined straight line $H_1(T)$ comes to zero at a lower temperature than $H_2(T)$ and with decreasing of the temperature crosses the line $H_2(T)$ only under the condition $\xi'_{0\parallel}\xi'_{0\perp} > \xi_{0\parallel}\xi_{0\perp}$. If $T_{c1} < T_{c2}$, the above condition has the form $\xi'_{0\parallel}\xi'_{0\perp}T_{c2} > \xi_{0\parallel}\xi_{0\perp}T_{c1}$ and remains for the massive sample as well. The influence of the film boundaries on the crossing point position becomes noticeable if $\xi_{0\parallel}^2/d^2 \gtrsim \Delta T_c/T_c$. For $T_{c1} > T_{c2}$ the kink of $H_{c2}(T)$ is absent for a massive sample and appears for a thin film if $T_1(d) < T_{c2}$. Under the condition $\xi'_{0\parallel}\xi'_{0\perp}T_{c2} < \xi_{0\parallel}\xi_{0\perp}T_{c1}$ and $T_{c1} > T_{c2}$ the kink occurs for a massive sample and disappears with decreasing a film thickness, when the condition $T_1(d) < T_{c2}$ becomes valid.

In the case of diffusively scattering boundaries the boundary conditions are

$$\eta_{1|x=\pm d} = 0 \quad , \quad \eta_{2|x=\pm d} = 0. \quad (54)$$

As just above, let's firstly neglect the difference between T_{c1} , T_{c2} and compare linear functions $H_1(T)$, $H_2(T)$ which are related with the solutions $\eta_1 = \cos(\pi x/2d)\eta_{10}(y)$, $\eta_2 = 0$ and $\eta_1 = 0$, $\eta_2 = \cos(\pi x/2d)\eta_{20}(y)$ respectively. These solutions satisfy the Ginzburg-Landau equations following from (52) together with the boundary conditions (54). Here $H_{c2} = \max(H_1(T), H_2(T))$. Since for the case in question one has

$$\frac{\Delta T_1}{\Delta T_2} = \frac{\xi_{0\parallel}^2}{\xi_{0\parallel}'^2} \quad , \quad \frac{H'_1(T)}{H'_2(T)} = \frac{\xi'_{0\perp}\xi'_{0\parallel}}{\xi_{0\perp}\xi_{0\parallel}}, \quad (55)$$

the condition for $H_{c2}(T)$ to have a kink becomes much more restrictive than in the case of specular reflection. Indeed, if $\xi_{0\parallel} > \xi'_{0\parallel}$, the kink takes place under the condition $\xi'_{0\perp}/\xi_{0\perp} > \xi_{0\parallel}/\xi'_{0\parallel} > 1$. In the opposite case $\xi_{0\parallel} < \xi'_{0\parallel}$ the kink occurs if $\xi'_{0\perp}/\xi_{0\perp} < \xi_{0\parallel}/\xi'_{0\parallel} < 1$. The latter condition means, in particular, that if the relation $\xi'_{0\perp} < \xi_{0\perp}$ holds for the coherence lengths in the perpendicular to the basal plane direction, the opposite relation $\xi'_{0\parallel} > \xi_{0\parallel}$ must be valid for the coherence lengths in the parallel direction. Though the relationship of such kind is, in principle, admissible, it is a quite strict demand [41]. It is in contrast with the result of previous section for two-component order parameter and the same boundary conditions (54), that the kink in the temperature dependence of the upper critical field always takes place for a thin film.

If $T_{c1} \neq T_{c2}$ and, for example, $T_{c1} > T_{c2}$, then the kink occurring for a massive sample under the condition $\xi'_{0\parallel}\xi'_{0\perp}T_{c2} < \xi_{0\parallel}\xi_{0\perp}T_{c1}$, remains at $\xi_{0\parallel}^2T_{c1} < \xi_{0\parallel}'^2T_{c2}$ for a thin film with diffusively scattering boundaries too. In the opposite case $\xi_{0\parallel}^2T_{c1} > \xi_{0\parallel}'^2T_{c2}$ the kink will disappear with decreasing of film thickness, when $T_2(d) > T_1(d)$.

V. CONCLUSIONS

Boundary conditions for the unconventional superconducting order parameter have been derived on the basis of microscopic theory for specularly reflecting boundaries. Using these boundary conditions (and those for diffusive scattering) for the problem of the upper critical field in a superconducting film, the appearance of a kink in a temperature dependence of $H_{c2}(T)$ has been examined. The presence or absence of a kink depends upon the ratios of coefficients at gradient terms in the Ginzburg-Landau functional and upon the quality of boundaries (specular reflection or diffusive scattering). If due to some other reasons the kink in a temperature dependence of $H_{c2}(T)$ takes place even for a massive homogeneous superconducting sample, the study of the location of a kink point in a thin film from the same compound may give a useful information about the type of pairing and the relations between the Ginzburg-Landau coefficients.

In the case of diffusively scattering boundaries and a two-component superconducting order parameter the kink turns out to be always present for the crystalline axes and magnetic field orientations considered above. Then the location of a kink point is qualitatively defined by the condition $d \sim \xi(T)$. At the same time in the case of accidental degeneracy the kink of $H_{c2}(T)$ in a thin film occurs due to the influence of diffusively scattering boundaries only under quite hard restrictions for the relative values of the coefficients at gradient terms.

For a two-component order parameter and $\varepsilon \neq 0$ the kink, strictly speaking, takes place only for considered above orientation of a magnetic field perpendicular to a crystalline axis of high symmetry. But for small enough values of ε and μ a smooth behaviour of the curve $H_{c2}(T)$ may exhibit an abrupt change of slope resembling the kink very much.

Recently incommensurate structural macroscopic modulations in heavy fermion UPt_3 have been observed along several crystalline directions [29]. Proceeding from the consideration of a thin film as the simplest model for studying the influence of an inhomogeneity on the sample properties, it is natural to suppose that for the appropriate orientations of a magnetic field smooth inhomogeneities of macroscopic scale may lead to the kink of $H_{c2}(T)$ as well. Note, that in the case of a thin superconducting film and of two-component order parameter the splitting of the superconducting transition in the absence of magnetic field may also be provoked due to the boundary conditions [1,42,43]. So, it is possible to consider the structural macroscopic modulations as one of the probable sources for the kink of $H_{c2}(T)$ and for the splitting of the critical temperature in UPt_3 .

After this article had already been submitted a paper by K.V.Samokhin appeared in Zh.Eksp.Teor.Fiz. **107**, 906 (1995), where the boundary conditions for unconventional superconductors were also considered and applied to the problem of the surface critical field H_{c3} .

The research described in this publication was made possible in part by Grant No M2D000 from the International Science Foundation.

APPENDIX

It is convenient to look for the minimal eigenvalue $\tilde{a}$ of the problem (30) using the perturbation theory in the parameter ε and transforming the problem to the form

$$\hat{H}_0\Psi + \hat{V}\Psi = \tilde{a}\Psi \quad (\text{A.1})$$

where

$$\Psi = \begin{pmatrix} \eta_1 \\ \eta_2 \end{pmatrix}, \quad \hat{V} = \begin{pmatrix} 0 & -2\varepsilon\partial_{xy} \\ -2\varepsilon\partial_{xy} & 0 \end{pmatrix},$$

$$\hat{H}_0 = \begin{pmatrix} -(1+\nu)\partial_x^2 + y^2 - (1-\nu)\partial_y^2 & 0 \\ 0 & -(1-\nu)\partial_x^2 + y^2 - (1+\nu)\partial_y^2 \end{pmatrix}. \quad (\text{A.2})$$

In terms of the operators

$$\hat{A} = \frac{i\sqrt{1-\nu}\partial_y + iy}{\sqrt{2}(1-\nu)^{1/4}}, \quad \hat{A}^+ = \frac{i\sqrt{1-\nu}\partial_y - iy}{\sqrt{2}(1-\nu)^{1/4}}, \quad \hat{B} = \frac{i\sqrt{1+\nu}\partial_y + iy}{\sqrt{2}(1+\nu)^{1/4}}, \quad \hat{B}^+ = \frac{i\sqrt{1+\nu}\partial_y - iy}{\sqrt{2}(1+\nu)^{1/4}} \quad (\text{A.3})$$

which satisfy the conditions $[\hat{A}, \hat{A}^+] = 1, [\hat{B}, \hat{B}^+] = 1$, the unperturbed Hamiltonian reads

$$\hat{H}_0 = \begin{pmatrix} -(1+\nu)\partial_x^2 + 2\sqrt{1-\nu}(\hat{A}^+\hat{A} + \frac{1}{2}) & 0 \\ 0 & -(1-\nu)\partial_x^2 + 2\sqrt{1+\nu}(\hat{B}^+\hat{B} + \frac{1}{2}) \end{pmatrix} \quad (\text{A.4})$$

From Eq.(A.4) one can see that a complete orthonormal set of eigenfunctions of the operator $\hat{H}_0$ may be represented as a set $\{\Psi_{mn}\} = \{\Psi_{mn}^A, \Psi_{mn}^B\}$, where

$$\Psi_{mn}^A = \begin{pmatrix} g_m^A f_n^A \\ 0 \end{pmatrix}, \quad \Psi_{mn}^B = \begin{pmatrix} 0 \\ g_m^B f_n^B \end{pmatrix}. \quad (\text{A.5})$$

Here $g_m^A(x), g_m^B(x)$ – the orthonormal eigenfunctions of the operator ∂_x^2 :

$$\partial_x^2 g_m^A = -\lambda_m^A g_m^A, \quad \partial_x^2 g_m^B = -\lambda_m^B g_m^B \quad (\text{A.6})$$

They are supposed to be defined at the segment $[-L, L]$ and to satisfy the boundary conditions for η_1, η_2 respectively.

The functions $f_n^A(y), f_n^B(y)$ are the orthonormal wave functions of harmonic oscillators satisfying the conditions $\hat{A}^+ \hat{A} f_n^A(y) = n f_n^A(y), \hat{B}^+ \hat{B} f_n^B(y) = n f_n^B(y)$. They may be represented as follows

$$f_0^A = \frac{1}{\pi^{1/4}(1-\nu)^{1/8}} e^{-\frac{y^2}{2(1-\nu)^{1/2}}}, \quad \hat{A} f_0^A = 0, \quad f_n^A = \frac{1}{(n!)^{1/2}} (\hat{A}^+)^n f_0^A \quad (\text{A.7})$$

$$f_0^B = \frac{1}{\pi^{1/4}(1+\nu)^{1/8}} e^{-\frac{y^2}{2(1+\nu)^{1/2}}}, \quad \hat{B} f_0^B = 0, \quad f_n^B = \frac{1}{(n!)^{1/2}} (\hat{B}^+)^n f_0^B \quad (\text{A.8})$$

For the perturbation operator one has

$$(\Psi_{mn}^A)^+ \hat{V} \Psi_{kl}^A = 0, \quad (\Psi_{mn}^B)^+ \hat{V} \Psi_{kl}^B = 0, \quad (\Psi_{mn}^B)^+ \hat{V} \Psi_{kl}^A = -2\varepsilon(g_m^{B*} \partial_x g_k^A)(f_n^{B*} \partial_y f_l^A) \quad (\text{A.9})$$

Due to relations (A.5), (A.9), the expression for the minimal value of $\tilde{a}$ is $\tilde{a} = \min\{E^A, E^B\}$, where the quantities E^A, E^B are reduced in the second order of perturbation theory in the operator $\hat{V}$ to the form

$$E^A = E_{00}^A - \sum_{m,n} \frac{4\varepsilon^2 |\langle g_m^B | \partial_x | g_0^A \rangle|^2 |\langle f_n^B | \partial_y | f_0^A \rangle|^2}{E_{mn}^B - E_{00}^A} \quad (\text{A.10})$$

$$E^B = E_{00}^B - \sum_{m,n} \frac{4\varepsilon^2 |\langle g_m^A | \partial_x | g_0^B \rangle|^2 |\langle f_n^A | \partial_y | f_0^B \rangle|^2}{E_{mn}^A - E_{00}^B} \quad (\text{A.11})$$

Eigenvalues of the unperturbed Hamiltonian $\hat{H}_0$ may be written as

$$\begin{aligned} E_{mn}^A &= (1 + \nu) \lambda_m^A + 2\sqrt{1 - \nu} (n + \frac{1}{2}) \\ E_{mn}^B &= (1 - \nu) \lambda_m^B + 2\sqrt{1 + \nu} (n + \frac{1}{2}) \end{aligned} \quad (\text{A.12})$$

Inserting (A.7), (A.8) into the matrix element $\langle f_n^A | \partial_y | f_0^B \rangle$, one gets

$$\begin{aligned} \langle f_n^A | \partial_y | f_0^B \rangle &= \int_{-\infty}^{\infty} f_n^{A*} \partial_y f_0^B dy = \\ &= \frac{-i^n (1 - \nu)^{n/4}}{(n!)^{1/2} 2^{n/2} \pi^{1/2} (1 - \nu^2)^{1/8} (1 + \nu)^{1/2}} \int_{-\infty}^{\infty} y e^{-\frac{y^2}{2(1+\nu)^{1/2}}} \left(\frac{y}{(1 - \nu)^{1/2}} - \partial_y \right)^n e^{-\frac{y^2}{2(1-\nu)^{1/2}}} dy \end{aligned} \quad (\text{A.13})$$

The relation

$$I = \int_{-\infty}^{\infty} dy e^{-\frac{\beta y^2}{2}} y (\alpha y - \partial_y)^m e^{-\frac{\alpha y^2}{2}} = \sqrt{2\pi} 2^{\frac{m+1}{2}} \alpha^{\frac{m+1}{2}} \frac{(\alpha - \beta)^{\frac{m-1}{2}}}{(\alpha + \beta)^{\frac{m}{2}+1}} m!! \quad , \quad m = 1, 3, \dots \quad (\text{A.14})$$

permits to transform (A.13) to

$$\langle f_n^A | \partial_y | f_0^B \rangle = \begin{cases} 0 & , \quad n = 0, 2, 4, \dots \\ -\frac{i^n \sqrt{2} (1 - \nu)^{3/8} (1 + \nu)^{1/8} (n!!) C^{n/2} (\text{sgn} \nu)^{(n-1)/2}}{(n!)^{1/2} (\sqrt{1 + \nu} + \sqrt{1 - \nu})^{1/2} |\nu|^{1/2}} & , \quad n = 1, 3, 5, \dots, \end{cases} \quad (\text{A.15})$$

where

$$C = \left| \frac{\sqrt{1 + \nu} - \sqrt{1 - \nu}}{\sqrt{1 + \nu} + \sqrt{1 - \nu}} \right| = \frac{|\nu|}{1 + (1 - \nu^2)^{1/2}}. \quad (\text{A.16})$$

The expression for the matrix element $\langle f_n^B | \partial_y | f_0^A \rangle$ may be obtained from (A.15) by changing $\nu \rightarrow -\nu$.

With the aid of (A.12), (A.15) the Eq.(A.11) is reduced to

$$E^B = (1 - \nu) \lambda_0^B + \sqrt{1 + \nu} -$$

$$-\frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \sum_{\substack{m=0,1,2,\dots \\ n=1,3,5,\dots}} \frac{|<g_m^A|\partial_x|g_0^B>|^2 C^{n-1}(n!!)^2}{n! \left[n + \frac{1}{2} \left(1 - \sqrt{\frac{1+\nu}{1-\nu}} \right) + \frac{1}{2} \sqrt{1-\nu} \left(\frac{1+\nu}{1-\nu} \lambda_m^A - \lambda_0^B \right) \right]} \quad (A.17)$$

The sum over n is calculated along the following way

$$\begin{aligned} \sum_{n=1,3,\dots} \frac{C^{n-1}(n!!)^2}{n!(n+\lambda)} &= \sum_{n=1,3,\dots} \int_0^1 \frac{C^{n-1}(n!!)^2 t^{n+\lambda-1}}{n!} dt = \int_0^1 t^\lambda \sum_{n=1,3,\dots} \frac{(Ct)^{n-1}(n!!)^2}{n!} dt = \\ &= \int_0^1 \frac{t^\lambda}{(1-(Ct)^2)^{3/2}} dt = \frac{1}{C^{\lambda+1}} \int_0^C \frac{t^\lambda}{(1-t^2)^{3/2}} dt = \frac{1}{\sqrt{1-C^2}} - \frac{\lambda}{C^{\lambda+1}} \int_0^{\arcsin C} \sin^\lambda(y) dy. \end{aligned} \quad (A.18)$$

Introducing the designation $\beta(\nu) = [1 - (1-\nu)^{1/2}/(1+\nu)^{1/2}]/2$ and using (A.18), one can transform (A.17) to the following expression

$$\begin{aligned} E^B &= \sqrt{1+\nu} + (1-\nu)\lambda_0^B - \\ &-\frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 \frac{t^{\beta(-\nu)} dt}{(1-C^2 t^2)^{3/2}} \sum_{m=0,1,2,\dots} |<g_m^A|\partial_x|g_0^B>|^2 t^{\gamma_{m0}^{AB}(\nu)}, \end{aligned} \quad (A.19)$$

where $\gamma_{m0}^{AB}(\nu) = \sqrt{1-\nu} [\lambda_m^A(1+\nu)/(1-\nu) - \lambda_0^B]/2$.

For E^A one gets in analogous way

$$\begin{aligned} E^A &= \sqrt{1-\nu} + (1+\nu)\lambda_0^A - \\ &-\frac{\varepsilon^2(1-C^2)^{3/2}}{(1-\nu^2)^{1/2}} \int_0^1 \frac{t^{\beta(\nu)} dt}{(1-C^2 t^2)^{3/2}} \sum_{m=0,1,2,\dots} |<g_m^B|\partial_x|g_0^A>|^2 t^{\gamma_{m0}^{BA}(\nu)}, \end{aligned} \quad (A.20)$$

where $\gamma_{m0}^{BA}(\nu) = \sqrt{1+\nu} [\lambda_m^B(1-\nu)/(1+\nu) - \lambda_0^A]/2$.

Since one should use now the explicit expressions for functions g_m^A , g_m^B , below we consider the cases of specularly reflecting and diffusively scattering boundaries separately.

a) Specularly reflecting boundaries

For the given crystal orientation the boundary conditions for functions g_m^A , g_m^B in the case of specularly reflection are

$$g_m^A|_{x=\pm L} = 0 \quad , \quad \partial_x g_m^B|_{x=\pm L} = 0 \quad (A.21)$$

The orthonormal eigenfunctions of the operator ∂_x^2 satisfying the conditions (A.21), constitute the sets

$$g_m^A = \frac{1}{\sqrt{L}} \cos(k_{m+1}x + \phi_{m+1}) \quad , \quad g_m^B = \frac{1}{\sqrt{L}} \sin(k_m x + \phi_m) \quad (A.22)$$

where $k_m = \frac{\pi}{2L}m$, $\phi_m = \frac{\pi}{2}(m+1)$, $m = 0, 1, 2, \dots$

Substituting (A.22) into (A.19), (A.20) and taking into account relations

$$\langle g_m^A | \partial_x | g_0^B \rangle = 0 \quad , \quad \langle g_m^B | \partial_x | g_0^A \rangle = \begin{cases} 0 & , m \neq 1 \\ -k_1 & , m = 1 \end{cases} \quad (\text{A.23})$$

one obtains

$$E^B = \sqrt{1 + \nu} \quad (\text{A.24})$$

$$E^A = \sqrt{1 - \nu} + \left(\frac{\pi}{2L} \right)^2 \left(1 + \nu - \frac{\varepsilon^2 (1 - C^2)^{3/2}}{(1 - \nu^2)^{1/2}} \int_0^1 \frac{dt t^{\beta(\nu)}}{(1 - C^2 t^2)^{3/2}} t^{\frac{-\nu \pi^2}{4L^2 \sqrt{1+\nu}}} \right) \quad (\text{A.25})$$

Eq.(A.25), which is applicable for small enough ε and any admissible value of ν , is reduced in the limit $|\nu| \ll L^2$ to the following expression

$$|\nu| \ll L^2 \quad : \quad E^A = \sqrt{1 - \nu} + \left(\frac{\pi}{2L} \right)^2 \left(1 + \nu - \frac{\varepsilon^2 (1 - C^2)^{3/2}}{(1 - \nu^2)^{1/2}} \int_0^1 \frac{dt t^{\beta(\nu)}}{(1 - C^2 t^2)^{3/2}} \right) \quad (\text{A.26})$$

b) Diffusively scattering boundaries

Under the boundary conditions

$$g_m^A|_{x=\pm L} = 0 \quad , \quad g_m^B|_{x=\pm L} = 0 \quad (\text{A.27})$$

the corresponding eigenfunctions of the operator ∂_x^2 may be written as

$$g_m^A = g_m^B = \frac{1}{\sqrt{L}} \cos(k_{m+1}x + \phi_{m+1}) \quad , \quad (\text{A.28})$$

where $k_m = m\pi/2L$, $\phi_m = (m+1)\pi/2$, $m = 0, 1, 2, \dots$

From (A.28) one gets the following expressions for matrix elements

$$\begin{aligned} \langle g_m^A | \partial_x | g_0^B \rangle &= \frac{1}{L} \int_{-L}^L \cos(k_{m+1}x + \phi_{m+1}) \partial_x \cos(k_1x + \phi_1) dx = \\ &= \frac{2k_1}{\pi} (1 - (-1)^m) \left(\frac{1}{m+2} + \frac{1}{m} \right) \quad m = 0, 1, 2, \dots \end{aligned} \quad (\text{A.29})$$

and for the eigenvalues of the operator ∂_x^2 : $\lambda_0^B = k_1^2 = \left(\frac{\pi}{2L} \right)^2$, $\lambda_m^A = k_{m+1}^2 = \left(\frac{\pi}{2L} \right)^2 (m+1)^2$.

With the aid of (A.29) the relation (A.19) takes the form

$$\begin{aligned} E^B &= \sqrt{1 + \nu} + (1 - \nu) \left(\frac{\pi}{2L} \right)^2 - \\ &- \frac{\varepsilon^2 (1 - C^2)^{3/2}}{(1 - \nu^2)^{1/2}} \int_0^1 \frac{dt t^{\beta(-\nu)}}{(1 - C^2 t^2)^{3/2}} \sum_{k=1}^{\infty} \frac{1}{L^2} \frac{k^2}{\left(k^2 - \frac{1}{4} \right)^2} t^{\left(\frac{\pi}{2L} \right)^2 \frac{\sqrt{1-\nu}}{2} \left(\left(\frac{1+\nu}{1-\nu} \right) 4k^2 - 1 \right)} \end{aligned} \quad (\text{A.30})$$

Since $g_m^A = g_m^B$, the expression for E^A may be obtained from E^B simply by substitution $\nu \rightarrow -\nu$. It is easy to see that the curves $E^B(L)$ and $E^A(L)$ cross each other. Designating $\tilde{\nu} = |\nu| \text{sgn}(T - T_k)$, where T_k is the point of crossing, one obtains for $\tilde{a} = \min(E^A, E^B)$:

$$\tilde{a} = \sqrt{1 + \tilde{\nu}} + (1 - \tilde{\nu}) \left(\frac{\pi}{2L} \right)^2 - \frac{\varepsilon^2(1 - C^2)^{3/2}}{L^2(1 - \nu^2)^{1/2}} \int_0^1 \frac{dt t^{\beta(-\tilde{\nu})}}{(1 - C^2 t^2)^{3/2}} \sum_{k=1}^{\infty} \frac{k^2}{\left(k^2 - \frac{1}{4}\right)^2} t^{\left(\frac{\pi}{2L}\right)^2 \frac{\sqrt{1-\tilde{\nu}}}{2} \left(\left(\frac{1+\tilde{\nu}}{1-\tilde{\nu}}\right) 4k^2 - 1\right)} \quad (\text{A.31})$$

Eq.(A.31) can be simplified in the limits of large and small values of parameter L . For $L^2 \gg 1$ it follows

$$L^2 \gg 1 \quad : \quad \tilde{a} = \sqrt{1 + \tilde{\nu}} + \left(\frac{\pi}{2L} \right)^2 \left(1 - \tilde{\nu} - \frac{\varepsilon^2(1 - C^2)^{3/2}}{(1 - \nu^2)^{1/2}} \int_0^1 \frac{dt t^{\beta(-\tilde{\nu})}}{(1 - C^2 t^2)^{3/2}} \right), \quad (\text{A.32})$$

where the relation

$$\sum_{k=1}^{\infty} \frac{k^2}{\left(k^2 - \frac{1}{4}\right)^2} = \frac{\pi^2}{4}$$

has been taken into account. In the opposite limit $L^2 \ll 1$ the integral in (A.31) is transformed as follows

$$\begin{aligned} \frac{1}{L^2} \int_0^1 dt \frac{t^{\beta(-\tilde{\nu})}}{(1 - C^2 t^2)^{3/2}} t^{\delta(\tilde{\nu})} &= \frac{8}{\pi^2 \sqrt{1 - \tilde{\nu}} \left(\frac{1+\tilde{\nu}}{1-\tilde{\nu}} 4k^2 - 1\right)} \int_0^1 \frac{t^{\beta(-\tilde{\nu})} dt}{(1 - C^2 t^2)^{3/2}} t^{\delta(\tilde{\nu})} = \\ &= \frac{8}{\pi^2 \sqrt{1 - \tilde{\nu}} \left(\frac{1+\tilde{\nu}}{1-\tilde{\nu}} 4k^2 - 1\right)} \left(\frac{1}{(1 - C^2)^{3/2}} - \int_0^1 t^{\delta(\tilde{\nu})} d \left(\frac{t^{\beta(-\tilde{\nu})}}{(1 - C^2 t^2)^{3/2}} \right) \right) \xrightarrow{L \rightarrow 0} \\ &\rightarrow \frac{8}{\pi^2 \sqrt{1 - \tilde{\nu}} \left(\frac{1+\tilde{\nu}}{1-\tilde{\nu}} 4k^2 - 1\right)} \frac{1}{(1 - C^2)^{3/2}} \end{aligned} \quad (\text{A.33})$$

Here

$$\delta(\tilde{\nu}) = \left(\frac{\pi}{2L} \right)^2 \frac{\sqrt{1 - \tilde{\nu}}}{2} \left(\left(\frac{1 + \tilde{\nu}}{1 - \tilde{\nu}} \right) 4k^2 - 1 \right) \quad (\text{A.34})$$

Then one has

$$L^2 \ll 1 \quad : \quad \tilde{a} = \left(\frac{\pi}{2L} \right)^2 (1 - \tilde{\nu}) + \sqrt{1 + \tilde{\nu}} \left(1 - \frac{2\varepsilon^2}{\pi^2(1 + \tilde{\nu})^2} \sum_{k=1}^{\infty} \frac{k^2}{\left(k^2 - \frac{1}{4}\right)^2} \frac{1}{\left(k^2 - \frac{(1-\tilde{\nu})}{4(1+\tilde{\nu})}\right)} \right) \quad (\text{A.35})$$

The sum presented here is

$$\sum_{k=1}^{\infty} \frac{k^2}{\left(k^2 - \frac{1}{4}\right)^2} \frac{1}{(k^2 - \gamma^2)} = \frac{\pi^2}{1 - 4\gamma^2} \left(1 - \frac{8\gamma \cot(\pi\gamma)}{\pi(1 - 4\gamma^2)} \right) \quad (\text{A.36})$$

From (A.35), (A.36) it follows

$$L^2 \ll 1 : \quad \tilde{a} = \left(\frac{\pi}{2L}\right)^2 (1 - \tilde{\nu}) + \sqrt{1 + \tilde{\nu}} \left(1 - \frac{\varepsilon^2}{(1 + \tilde{\nu})\tilde{\nu}} \left(1 - \frac{2}{\pi} \frac{\sqrt{1 - \nu^2}}{\tilde{\nu}} \cot \left(\frac{\pi}{2} \sqrt{\frac{1 - \tilde{\nu}}{1 + \tilde{\nu}}}\right)\right)\right) \quad (A.37)$$

REFERENCES

- [1] M.Sigrist, and K.Ueda, Rev.Mod.Phys. **63**, 239 (1991).
- [2] J.A.Sauls, Adv. Phys. **43**, 113 (1994).
- [3] R.Joint, V.P.Mineev, G.E.Volovik, and M.E.Zhitomirsky, Phys. Rev. B **42**, 2014 (1990).
- [4] D.-C.Chen and A.Garg, Phys.Rev.Lett. **70**, 1689 (1993)
- [5] R.Fisher et al., Phys.Rev.Lett **62**, 1411 (1989).
- [6] K.Hasselbach, L.Taillefer, and J.Flouquet, Phys.Rev.Lett. **63**, 93 (1989).
- [7] S.Adenwala et al., Phys.Rev.Lett.**65**, 2298 (1990).
- [8] S.-W.Lin, C.Jin, H.Zhang, J.B.Ketterson, D.M.Lee, D.G.Hinks, M.Levy, and B.K. Sarma, Phys.Rev.Lett. **49**, 10001 (1994).
- [9] B.Shivaram, J.Gannon Jr., and D.Hinks, Phys.Rev.Lett. **63**, 1723 (1989).
- [10] E.Vincent et al., J.Phys.Condens.Matter **3**, 3517 (1991).
- [11] V.Müller et al., Phys.Rev.Lett. **58**, 1224 (1987).
- [12] Y.Qian et al., Solid State Commun. **63**, 599 (1987).
- [13] A.Schenstrom et al., Phys.Rev.Lett. **62**, 332 (1989).
- [14] R.Kleiman et al., Phys.Rev.Lett. **62**, 328, (1989).
- [15] G.Bruls et al., Phys.Rev.Lett. **65**, 2294 (1990).
- [16] G.Bullock, B.Shivaram, and D.Hinks, Europhys.Lett. **21**, 357 (1993)
- [17] N.H. van Dijk et al., Phys.Rev. B**48**, 1299 (1993).
- [18] M.Boukny, G.L.Bullock, B.S.Shivaram, and D.Hinks, Phys.Rev.Lett. **73**, 1707 (1994).
- [19] D.Hess, T.Tokuyasu, and J.Sauls, J.Phys.Condens.Matter **1**, 8135 (1989).
- [20] K.Machida, M.Ozaki, J.Phys.Soc.Jpn. **58**, 2244 (1989).
- [21] T.A.Tokuyasu, D.W.Hess, and J.A.Sauls, Phys.Rev. B **41**, 8891 (1990).
- [22] Yu.S.Barash, A.S.Mel'nikov, Zh.Eksp.Teor.Fiz. **100**, 307 (1991) [Sov.Phys.JETP **73**, 170 (1991)].
- [23] K.Machida, M.Ozaki, Phys.Rev.Lett. **66**, 3293 (1991), **67**, 3732 (1991).
- [24] A.S.Mel'nikov, Zh.Eksp.Teor.Fiz. **101**, 1978 (1992) [Sov.Phys.JETP **74**, 1059 (1992)].
- [25] M.E.Zhitomirsky, and I.A.Lukyanchuk, Zh.Eksp.Teor.Fiz. **101**, 1954 (1992) [Sov.Phys. JETP **74**, 1046 (1992)].
- [26] M.E.Zhitomirsky, and I.A.Lukyanchuk, Sov.Phys.JETP Lett. **58**, 131 (1993).
- [27] Yu.S.Barash, A.S.Mel'nikov, Phys.Lett. A **186**, 259 (1994).
- [28] A.Garg, and D.C.Chen, Phys.Rev. B **49**, 479 (1994).
- [29] P.A.Midgley, S.M.Hayden, L.Taillefer, B.Bogenberger, and H.v.Löhneysen, Phys.Rev. Lett. **70**, 678 (1993).
- [30] G.E.Volovik, and L.P.Gor'kov, Zh.Eksp.Teor.Fiz **88**, 1412 (1985).
- [31] G.Eilenberger, Z.Phys. **214**, 195 (1968).
- [32] J.W.Serene, and D.Rainer, Phys.Rep. **101**, 221 (1984).
- [33] A.V.Zaitsev, Zh.Eksp.Teor.Fiz. **86**, 1742 (1984).
- [34] J.Kurkijarvi, D.Rainer, and J.A.Sauls, Can.J.Phys. **65**, 1440 (1987).
- [35] A.Millis, D.Rainer, and J.A.Sauls, Phys.Rev.B **38**, 4504 (1988).
- [36] Yu.S.Barash, A.V.Galaktionov, and A.D.Zaikin, in press.
- [37] A.V.Svidzinsky. *Spatially Nonhomogeneous Problems in the Superconductivity Theory*. Moscow, Nauka, 1982 [in Russian].
- [38] P.Wölfle, Phys.Lett.A **47**, 224 (1974).

- [39] E.A.Shapoval, Zh.Eksp.Teor.Fiz. **88**, 1073 (1985).
- [40] The boundary conditions for a tetragonal superconductor may be derived along the same way as it has been done in Sec.II for a hexagonal superconductor. For the given orientation with the normal to the boundary parallel to the axis x and in the case of specular reflection the boundary conditions are independent of the particular form of the basis functions of a representation (for the triplet pairing spins are assumed to be ordered along z -axis). Then one obtains $\eta'(0) = 0$ for $A_{1g}, A_{1u}, B_{1g}, B_{1u}$ representations, $\eta(0) = 0$ for the remaining one-dimensional representations of D_{4h} . For two-dimensional representations one gets Eq.(33).
- [41] Note that the same strict condition appears for the other orientation when the crystalline axis z is perpendicular to the boundary and $\mathbf{H} \parallel z$.
- [42] M.Sigrist, N.Ogawa and K.Ueda J.Phys.Soc.Jpn. **60**, 2341 (1991).
- [43] N.Ogawa, M.Sigrist, and K.Ueda, J.Phys.Soc.Jpn. **61**, 1730 (1992).

FIGURES

FIG. 1. The orientations of crystalline axes and the magnetic field relative to the film boundaries.

FIG. 2. The dependence $H_{c2}(T)$ for a film from superconductor with two-component order parameter for $\nu = \varepsilon = 0.5$ and film thickness $2d = 20\xi_0$ in the case of specularly reflecting surfaces (1) and of diffusive electron scattering (2).

TABLES

TABLE I.

Singlet		Triplet	
A_{1g}	1	A_{1u}	$\hat{c}p_z$
A_{2g}	$\text{Im}(p_x + ip_y)^6$	A_{2u}	$\hat{c}p_z \text{Im}(p_x + ip_y)^6$
B_{1g}	$p_z \text{Im}(p_x + ip_y)^3$	B_{1u}	$\hat{c} \text{Im}(p_x + ip_y)^3$
B_{2g}	$p_z \text{Re}(p_x + ip_y)^3$	B_{2u}	$\hat{c} \text{Re}(p_x + ip_y)^3$
E_{1g}	$p_z p_x, p_z p_y$	E_{1u}	$\hat{c}p_x, \hat{c}p_y$
E_{2g}	$2p_x p_y, p_x^2 - p_y^2$	E_{2u}	$\hat{c}2p_x p_y p_z, \hat{c}p_z(p_x^2 - p_y^2)$

TABLE 2.

Representation	$\phi_0 = n\pi/3$	$\phi_0 = (2n+1)\pi/6$
A_{1g}, A_{1u}	$\eta'(0) = 0$	$\eta'(0) = 0$
A_{2g}, A_{2u}	$\eta(0) = 0$	$\eta(0) = 0$
B_{1g}, B_{1u}	$\eta'(0) = 0$	$\eta(0) = 0$
B_{2g}, B_{2u}	$\eta(0) = 0$	$\eta'(0) = 0$
E_{1g}, E_{1u}	$\tilde{\eta}_1(0) = 0$	$\tilde{\eta}_1(0) = 0$
	$\tilde{\eta}'_2(0) = 0$	$\tilde{\eta}'_2(0) = 0$
E_{2g}, E_{2u}	$\tilde{\eta}_1(0) = 0$	$\tilde{\eta}_1(0) = 0$
	$\tilde{\eta}'_2(0) = 0$	$\tilde{\eta}'_2(0) = 0$

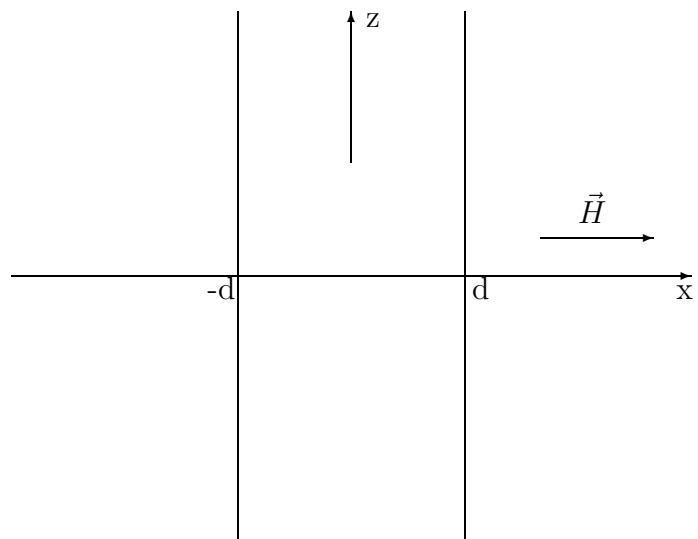


Fig. 1